



This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses. It should not therefore be construed as a warranty of specific properties of the products described or a warranty for fitness for a particular purpose.

Classified according to EU Directive 1999/45/EC

For further information see our "Material Safety Data Sheets".

Edition 4, 09.2011

The latest revised edition of this brochure is the English version, which is always published on our web site [www.uddeholm.com](http://www.uddeholm.com)



SS-EN ISO 9001  
SS-EN ISO 14001

## General

Uddeholm Hotvar is a high performance molybdenum-vanadium alloyed hot-work tool steel which is characterized by:

- high hot wear resistance
- very good high temperature properties
- high resistance to thermal fatigue
- very good temper resistance
- very good thermal conductivity

|                        |                                 |     |     |     |     |     |
|------------------------|---------------------------------|-----|-----|-----|-----|-----|
| Typical analysis %     | C                               | Si  | Mn  | Cr  | Mo  | V   |
|                        | 0.55                            | 1.0 | 0.8 | 2.6 | 2.3 | 0.9 |
| Standard specification | None                            |     |     |     |     |     |
| Delivery condition     | Soft annealed to approx. 210 HB |     |     |     |     |     |
| Colour code            | Red/brown                       |     |     |     |     |     |

## Improved tooling Performance

Uddeholm Hotvar is a specially premium hot work steel developed by Uddeholm to provide a very good performance in tooling up to 650°C. The alloy elements in Uddeholm Hotvar are balanced to give high hot wear resistance and good high temperature properties. Uddeholm Hotvar is manufactured by special techniques.

## Applications

Uddeholm Hotvar is a hot-work tool steel suitable for applications where hot wear and/or plastic deformation are the dominating failure mechanisms.

Applications and tools of especial interest:

- warm forging, dies and punches
- roll forging, rolling segments
- rock orbital forging, punches and dies
- upset forging, clamping tools
- progressive forging, dies
- axial closed die rolling, top and bottom dies
- cross forming, segments
- hot bending, tools
- hot calibration, tools
- zinc die casting, dies
- Al-tube extrusion

Recommended hardness level is 54–58 HRC.

For improving the wear resistance the tools can be plasma nitrided or nitrocarburized.

## Properties

All specimens are taken from the centre of a bar 115 mm Ø (4,5"). Unless otherwise is indicated all specimens were hardened at 1050°C (1920°F), quenched in air and tempered 2 + 2 h at 575°C (1070°F) to a hardness corresponding to 56 HRC.

## Physical data

Data at room and elevated temperatures.

| Temperature  | 20°C<br>(68°F)                    | 400°C<br>(750°F)                                  | 600°C<br>(1110°F)                                 |
|--|-----------------------------------|---|---|
| Density<br>kg/m <sup>3</sup><br>lbs/in <sup>3</sup>                  | 7 800<br>0.281                    | 7 700<br>0.277                                    | 7 600<br>0.274                                    |
| Modulus of elasticity<br>MPa<br>psi                                  | 210 000<br>30.5 × 10 <sup>6</sup> | 180 000<br>26.1 × 10 <sup>6</sup>                 | 140 000<br>20.3 × 10 <sup>6</sup>                 |
| Coefficient of thermal expansion per<br>°C from 20°C<br>°F from 68°F | –<br>–                            | 12.6 × 10 <sup>-6</sup><br>7.0 × 10 <sup>-6</sup> | 13.2 × 10 <sup>-6</sup><br>7.3 × 10 <sup>-6</sup> |
| Thermal conductivity<br>W/m °C<br>Btu in/(ft <sup>2</sup> h°F)       | 31<br>215                         | 33<br>230   | 33<br>230   |


## Mechanical properties

Approximate tensile strength at room temperature.

| Hardness                            | 54 HRC                              | 56 HRC                              | 58 HRC                              |
|-------------------------------------|-------------------------------------|-------------------------------------|-------------------------------------|
| Tensile strength<br>R <sub>m</sub>  | 2 100 MPa<br>136 tsi<br>305 000 psi | 2 200 MPa<br>142 tsi<br>320 000 psi | 2 300 MPa<br>149 tsi<br>335 000 psi |
| Yield strength<br>R <sub>p0,2</sub> | 1 800 MPa<br>117 tsi<br>260 000 psi | 1 820 MPa<br>119 tsi<br>265 000 psi | 1 850 MPa<br>121 tsi<br>270 000 psi |




HOT STRENGTH

Hot strength in longitudinal direction.

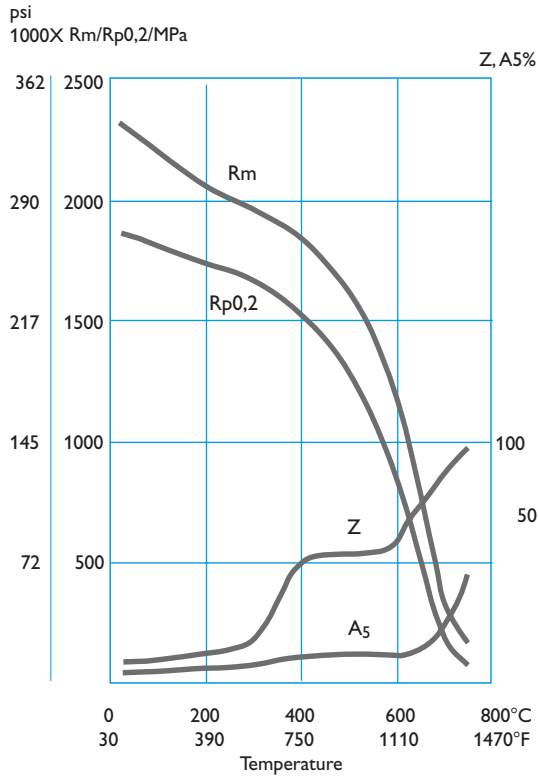


EFFECT OF TIME AT HIGH TEMPERATURE ON HARDNESS

The softening at high temperatures and different holding times are shown below. The specimens have first been hardened and tempered to 54, 56 and 58 HRC.

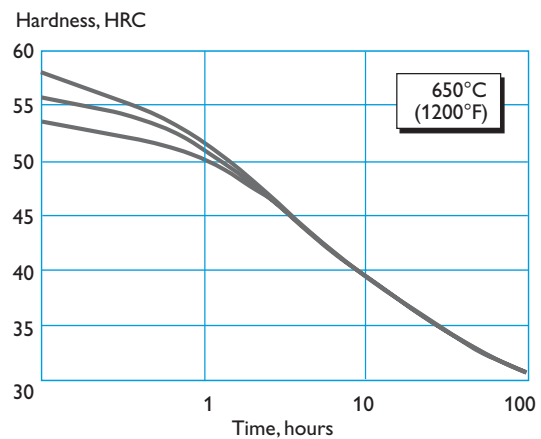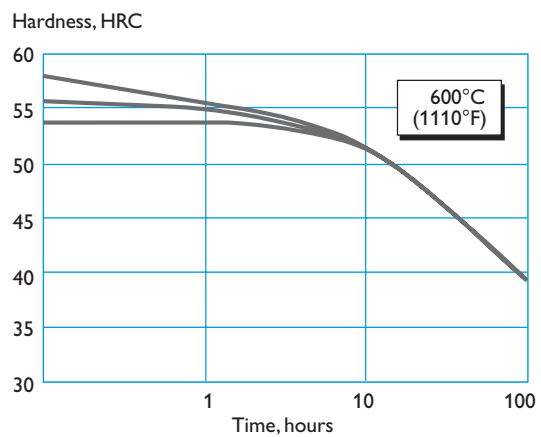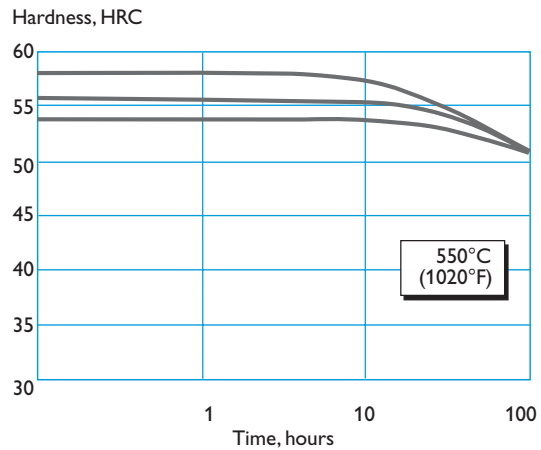

EFFECT OF TESTING TEMPERATURE ON IMPACT ENERGY

Charpy-V specimens, transverse direction.

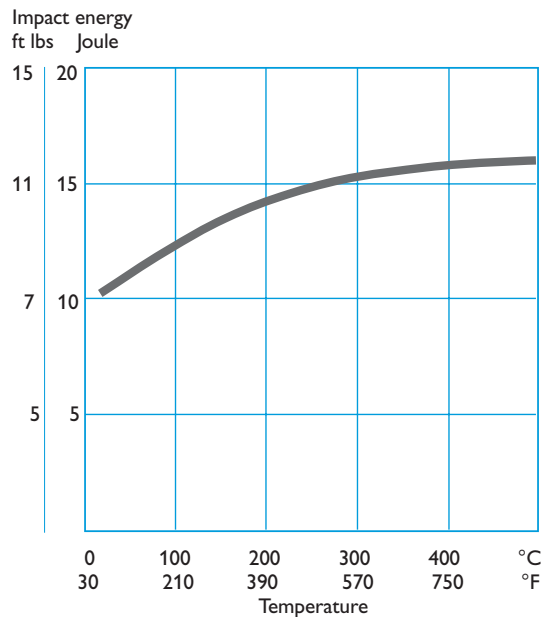

# Heat treatment— general recommendations

## Soft annealing

Protect the steel and heat through to 820°C (1500°F). Then cool in the furnace at 10°C (20°F) per hour to 600°C (1110°F), then freely in air.

## Stress relieving

After rough machining the tool should be heated through to 650°C (1200°F), holding time 2 hours. Cool slowly to 350°C (660°F), then freely in air.

## Hardening

*Pre-heating temperature:* first step at 480–600°C (895–1110°F), second step at 850 (1560°F).  
*Austenitizing temperature:* 1050–1070°C (1920–1960°F), normally 1050°C (1920°F) but when maximum hardness is required the normally temperature is 1070°C (1960°F).

| Temperature |      | Soaking*<br>time<br>minutes | Hardness before temp.<br>for Ø 25 mm (1") |       |
|-------------|------|-----------------------------|---|-------|
| °C          | °F   |                             | Oil                                       | Air   |
| 1050        | 1920 | 30                          | 61 ±1                                     | 59 ±1 |
| 1070        | 1960 | 20                          | 62 ±1                                     | 60 ±1 |

\* Soaking time = time at hardening temperature after the tool is fully heated through

*Protect the part against decarburization and oxidation during hardening.*

## Quenching media


- High speed gas/circulating atmosphere
- Vacuum (high speed gas with sufficient positive pressure)
- Martempering bath or fluidized bed at 450–550°C (840–1020°F)
- Martempering bath or fluidized bed at approx. 180–220°C (360–430°F)
- Warm oil, approx. 80°C (175°F)

*Note 1:* Temper the tool as soon as its temperature reaches 50–70°C (120–160°F).

*Note 2:* In order to obtain the optimum properties for the tool, the cooling rate should be fast, but not at a level that gives excessive distortion or cracks.


## CCT -GRAPH

Austenitizing temperature 1050°C (1920°F). Holding time 30 minutes.

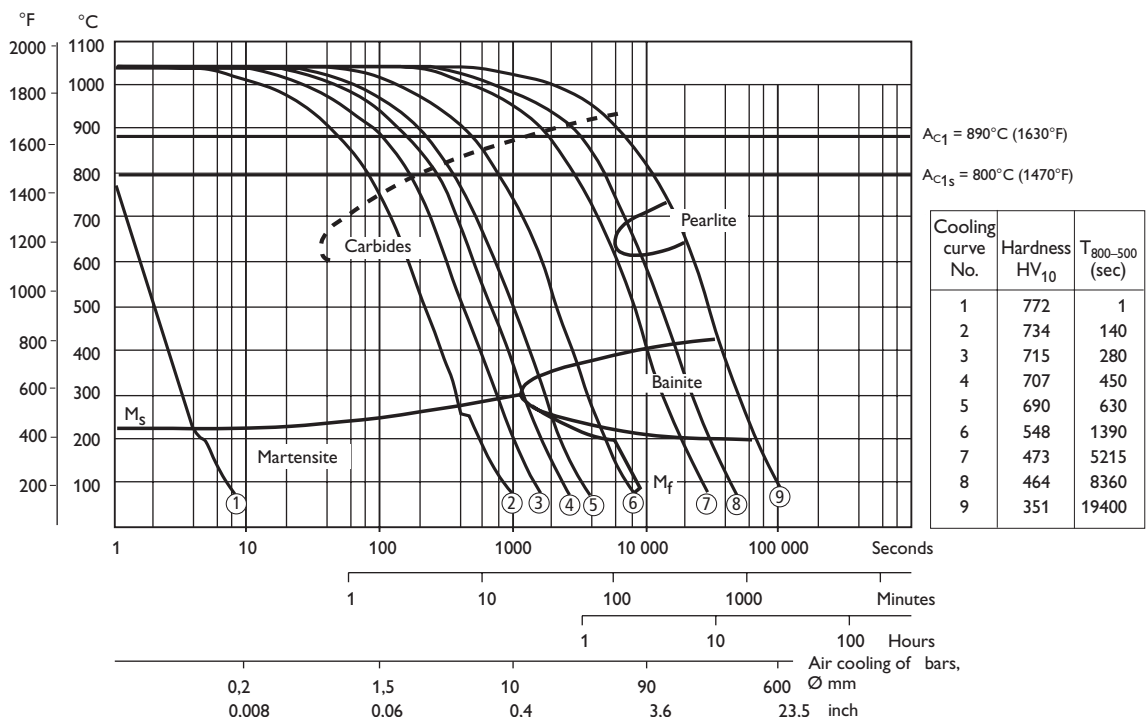

**HARDNESS, GRAIN SIZE AND RETAINED AUSTENITE AS FUNCTIONS OF AUSTENITIZING TEMPERATURE**


Samples Ø 25 mm (1 inch)

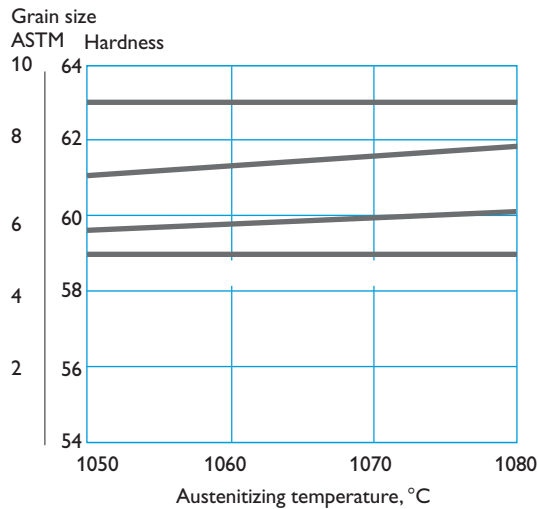

**Tempering**

Choose the tempering temperature according to the hardness required by reference to the tempering graph. Temper minimum twice with intermediate cooling to room temperature. Holding time at temperature minimum 2 h.

TEMPERING GRAPH

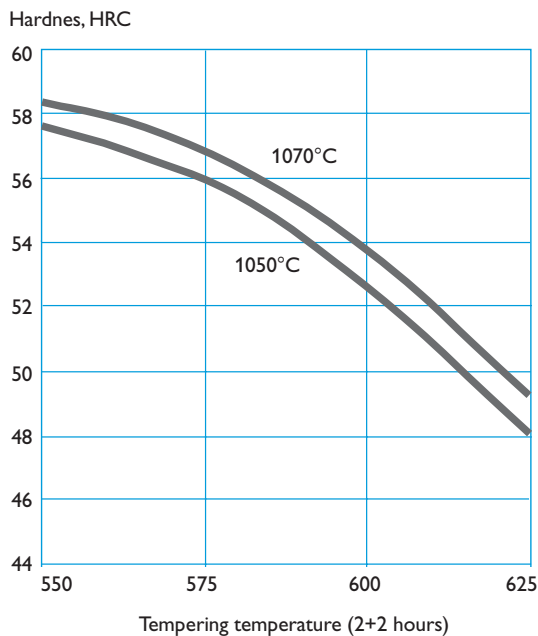

Tempering at 250°C (485°F), 2 + 2 h gives a hardness of 56–58 HRC.

**Dimensional changes during hardening and tempering**

During hardening and tempering the die is exposed to thermal as well as transformation stresses. This will inevitably result in dimensional changes and in the worse case distortion. It is therefore recommended to always leave enough machining allowance after machining before the die is hardened and tempered. Normally the size in the largest direction will shrink and the size in the smallest direction might increase, but this is also a matter of the die size, the die design as well as the cooling rate after hardening.

For Uddeholm Hotvar it is recommended to leave a machining allowance of 0.4 per cent of the dimension in length, width and thickness.

**Nitriding and nitrocarburizing**

Nitriding and nitrocarburizing result in a hard surface layer which is very resistant to wear and erosion. The nitrided layer is, however, brittle and may crack or spall when exposed to mechanical or thermal shock, the risk increasing with layer thickness. Before nitriding, the tool should be hardened and tempered at a temperature at least 50°C (90°F) above the nitriding temperature.

Nitriding in ammonia gas at 510°C (950°F) or plasma nitriding in a 75% hydrogen/25% nitrogen mixture at 480°C (895°F) both result in a surface hardness of about 1000 HV<sub>0.2</sub>. In general, plasma nitriding is the preferred method because of better control over nitrogen potential.

Uddeholm Hotvar e can also be nitrocarburized in either gas or salt bath. The surface hardness after nitrocarburizing is about 900 HV<sub>0.2</sub>.

DEPTH OF NITRIDING

| Process  | Time | Depth |        |
|--|------|-------|--------|
|  |      | mm    | inch   |
| Plasma nitriding<br>at 480°C (895°F)             | 10   | 0.18  | 0.0070 |
|  | 30   | 0.27  | 0.0106 |
| Nitrocarburizing<br>-in gas<br>at 580°C (1075°F) | 2.5  | 0.20  | 0.0080 |
|  |      |       |        |

It should be noted that Uddeholm Hotvar exhibits better nitridability than AISI H13. For this reason, the nitriding times for Uddeholm Hotvar should be shortened in relation to H13, otherwise there is a considerable risk that the case depth will be too great.

## Machining recommendations

The cutting data below are to be considered as guiding values, which must be adapted to existing local conditions.

More information can be found in the Uddeholm publication "Cutting data recommendation".

### Turning

| Cutting data parameters                    | Turning with carbide               |                                       | Turning with high speed steel<br>Fine turning |
|--|------------------------------------|---------------------------------------|---|
|  | Rough turning                      | Fine turning                          |   |
| Cutting speed ( $v_c$ )<br>m/min<br>f.p.m. | 150–170<br>490–560                 | 170–190<br>560–620                    | 20–25<br>65–80                                |
| Feed (f)<br>mm/r<br>i.p.r.                 | 0.2–0.4<br>0.008–0.016             | 0.05–0.2<br>0.002–0.008               | 0.05–0.3<br>0.002–0.012                       |
| Depth of cut ( $a_p$ )<br>mm<br>inch       | 2–4<br>0.08–0.16                   | 0.5–2<br>0.02–0.08                    | 0.5–3<br>0.02–0.12                            |
| Carbide designation<br>ISO<br>US           | P20–P30<br>C6–C5<br>Coated carbide | P10<br>C7<br>Coated carbide or cermet | –<br>–  |

## Milling

### FACE AND SQUARE SHOULDER MILLING

| Cutting data parameters                    | Milling with carbide               |                                       |
|--|------------------------------------|---------------------------------------|
|  | Rough milling                      | Fine milling                          |
| Cutting speed ( $v_c$ )<br>m/min<br>f.p.m. | 140–200<br>460–655                 | 260–240<br>850–785                    |
| Feed ( $f_z$ )<br>mm/tooth<br>inch/tooth   | 0.2–0.4<br>0.008–0.016             | 0.1–0.2<br>0.004–0.008                |
| Depth of cut ( $a_p$ )<br>mm<br>inch       | 2–5<br>0.08–0.2                    | –2<br>–0.08                           |
| Carbide designation<br>ISO<br>US           | P20–P40<br>C6–C5<br>Coated carbide | P10<br>C7<br>Coated carbide or cermet |

### END MILLING

| Cutting data parameters                    | Type of end mill                                    |   |  |
|--|---|---|--|
|  | Solid carbide                                       | Carbide indexable insert                            | High speed steel                                     |
| Cutting speed ( $v_c$ )<br>m/min<br>f.p.m. | 110–150<br>360–490                                  | 120–160<br>390–520                                  | 20–25 <sup>1)</sup><br>65–80 <sup>1)</sup>           |
| Feed ( $f_z$ )<br>mm/tooth<br>inch/tooth   | 0.03–0.2 <sup>2)</sup><br>0.001–0.008 <sup>2)</sup> | 0.08–0.2 <sup>2)</sup><br>0.003–0.008 <sup>2)</sup> | 0.05–0.35 <sup>2)</sup><br>0.002–0.014 <sup>2)</sup> |
| Carbide designation<br>ISO<br>US           | –<br>–  | P20–P30<br>C6–C5                                    | –<br>–   |

<sup>1)</sup> For coated high speed steel end mill  $v_c = 35–40$  m/min (115–130 f.p.m.)

<sup>2)</sup> Depending on radial depth of cut and cutter diameter

## Drilling

### HIGH SPEED STEEL TWIST DRILL

| Drill diameter |          | Cutting speed, $v_c$ |        | Feed, f   |             |
|----------------|----------|----------------------|--------|-----------|-------------|
| mm             | inch     | m/min                | f.p.m. | mm/r      | i.p.r.      |
| –5             | –3/16    | 14–16*               | 46–50* | 0.05–0.15 | 0.002–0.006 |
| 5–10           | 3/16–3/8 | 14–16*               | 46–50* | 0.15–0.20 | 0.006–0.008 |
| 10–15          | 3/8–5/8  | 14–16*               | 46–50* | 0.20–0.25 | 0.008–0.010 |
| 15–20          | 5/8–3/4  | 14–16*               | 46–50* | 0.25–0.35 | 0.010–0.014 |

\* For coated HSS drill  $v_c = 18–22$  m/min. ( 60–70 f.p.m.)

CARBIDE DRILL

| Cutting data parameters                            | Type of drill   |  |  |
|--|---|--|--|
|  | Indexable insert                                      | Solid carbide  | Carbide tip <sup>1)</sup>                            |
| Cutting speed (v <sub>c</sub> )<br>m/min<br>f.p.m. | 160–200<br>520–655                                    | 130–160<br>425–520                                   | 55–60<br>180–195                                     |
| Feed (f)<br>mm/r<br>i.p.r.                         | 0.03–0.12 <sup>2)</sup><br>0.0012–0.005 <sup>2)</sup> | 0.08–0.20 <sup>3)</sup><br>0.003–0.008 <sup>3)</sup> | 0.15–0.25 <sup>4)</sup><br>0.006–0.010 <sup>4)</sup> |

- <sup>1)</sup> Drill with replaceable or brazed carbide tip
- <sup>2)</sup> Feed rate for drill diameter 20–40 mm (0.8”–1.6”)
- <sup>3)</sup> Feed rate for drill diameter 5–20 mm (0.2”–0.8”)
- <sup>4)</sup> Feed rate for drill diameter 10–20 mm (0.4”–0.8”)

Grinding

A general grinding wheel recommendation is given below. More information can be found in the Uddeholm brochure “Grinding of Tool Steel” and can also be obtained from the grinding wheel manufacturer.

WHEEL RECOMMENDATION

| Type of grinding             | Soft annealed condition | Hardened condition |
|------------------------------|-------------------------|--------------------|
| Face grinding straight wheel | A 46 HV                 | A 46 GV            |
| Face grinding segments       | A 24 GV                 | A 36 GV            |
| Cylindrical grinding         | A 46 LV                 | A 60 KV            |
| Internal grinding            | A 46 JV                 | A 60 IV            |
| Profile grinding             | A 100 LV                | A 120 JV           |

Electrical-discharge machining

If spark-erosion is performed in the hardened and tempered condition, the white re-cast layer should be removed mechanically e.g. by grinding or stoning. The tool should then be given an additional temper at approx. 25°C (50°F) below the previous tempering temperature.

Welding

Welding of tool steel can be performed with good results if proper precautions are taken regarding elevated temperature, joint preparation, choice of consumables and welding procedure.

| Welding method         | TIG                    | MMA                    |
|------------------------|------------------------|------------------------|
| Working temperature    | 325–375°C<br>620–710°F | 325–375°C<br>620–710°F |
| Filler metal           | QRO 90 TIG-WELD        | QRO 90 WELD            |
| Hardness after welding | 48–53 HRC              | 48–53 HRC              |


| Heat treatment after welding |  |
|------------------------------|--|
| Hardened condition           | Temper at 20°C (40°F) below the original tempering temperature.  |
| Soft annealed condition      | Soft-anneal the material at 820°C (1500°F) in protected atmosphere. Then cool in the furnace at 10°C (20°F) per hour to 600°C (1110°F) then freely in air. |

More detailed information can be found in the Uddeholm brochure “Welding of Tool Steel”.

Further information

Please contact your local Uddeholm office for further information on the selection, heat treatment, application and availability of Uddeholm tool steel.



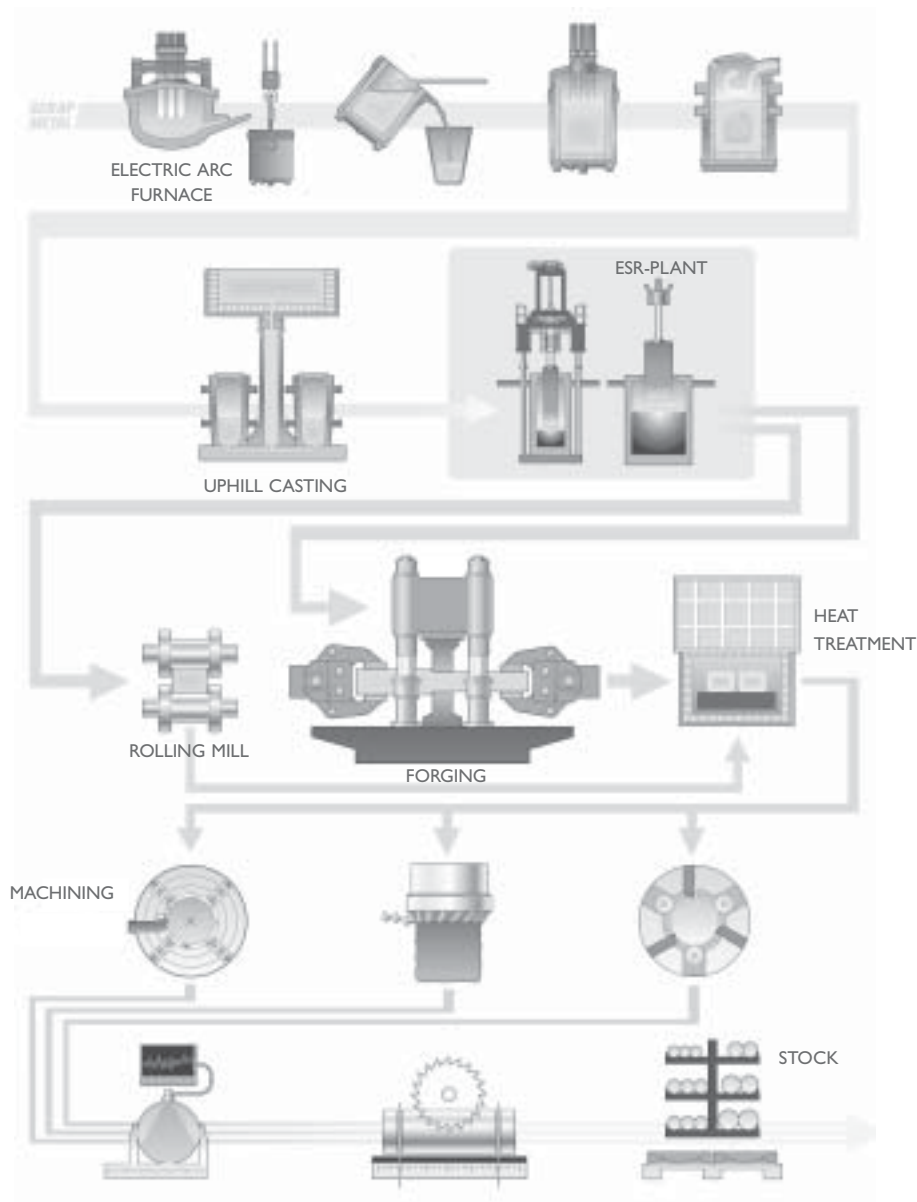

## The ESR Tool Steel Process

The starting material for our tool steel is carefully selected from high quality recyclable steel. Together with ferroalloys and slag formers, the recyclable steel is melted in an electric arc furnace. The molten steel is then tapped into a ladle.

The de-slagging unit removes oxygen-rich slag and after the de-oxidation, alloying and heating of the steel bath are carried out in the ladle furnace. Vacuum de-gassing removes elements such as hydrogen, nitrogen and sulphur.

### ESR PLANT

In uphill casting the prepared moulds are filled with a controlled flow of molten steel from the ladle.

From this, the steel can go directly to our rolling mill or to the forging press, but also to our ESR furnace where our most sophisticated steel grades are melted once again in an electro slag remelting process. This is done by melting a consumable electrode immersed in an overheated slag bath. Controlled solidification in the steel bath results in an ingot of high homogeneity, thereby

removing macro segregation. Melting under a protective atmosphere gives an even better steel cleanliness.

### HOT WORKING

From the ESR plant, the steel goes to the rolling mill or to our forging press to be formed into round or flat bars.


Prior to delivery all of the different bar materials are subjected to a heat treatment operation, either as soft annealing or hardening and tempering. These operations provide the steel with the right balance between hardness and toughness.

### MACHINING

Before the material is finished and put into stock, we also rough machine the bar profiles to required size and exact tolerances. In the lathe machining of large dimensions, the steel bar rotates against a stationary cutting tool. In peeling of smaller dimensions, the cutting tools revolve around the bar.

To safeguard our quality and guarantee the integrity of the tool steel we perform both surface- and ultrasonic inspections on all bars. We then remove the bar ends and any defects found during the inspection.



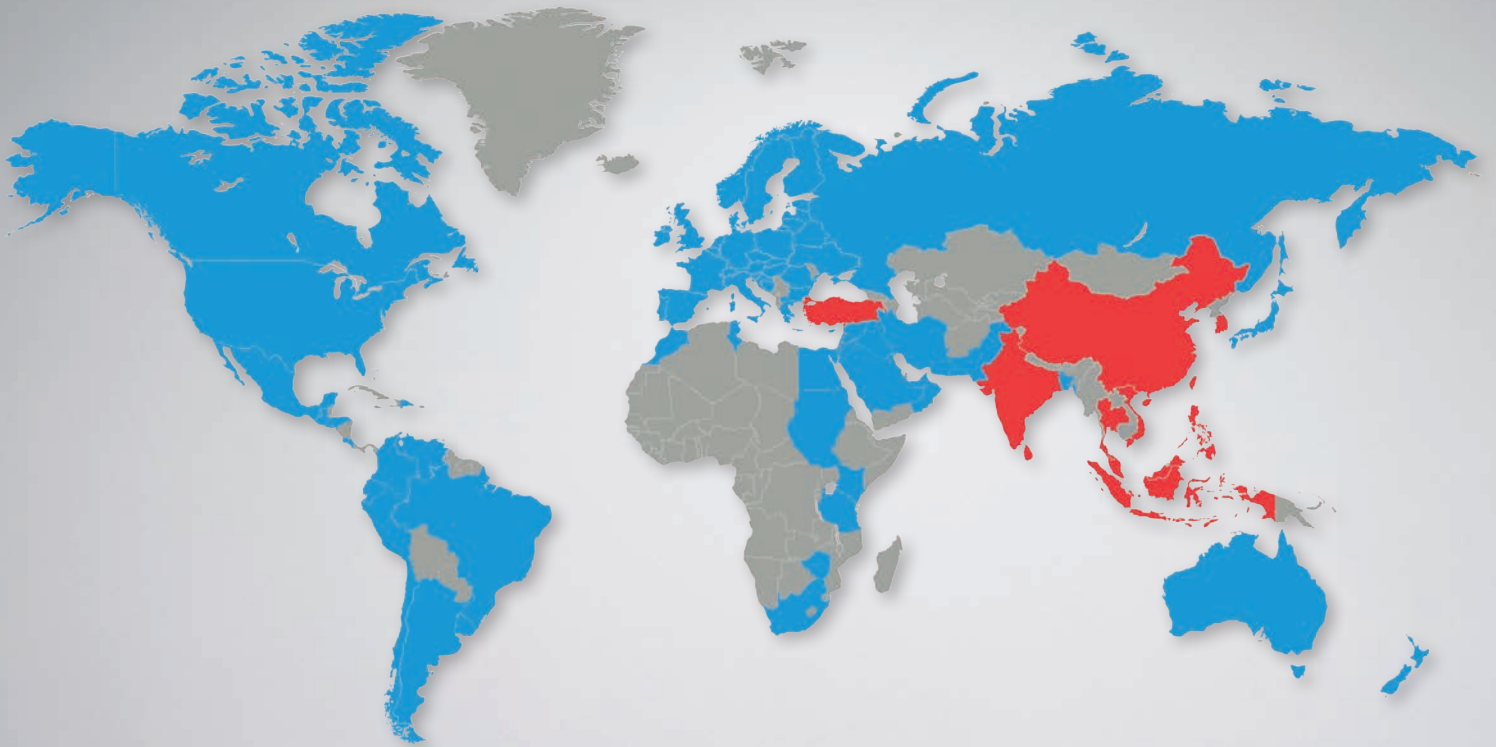

## Network of excellence

UDDEHOLM is present on every continent. This ensures you high-quality Swedish tool steel and local support wherever you are. ASSAB is our wholly-owned subsidiary and exclusive sales channel, representing Uddeholm in the Asia Pacific area. Together we secure our position as the world's leading supplier of tooling materials.

UDDEHOLM is the world's leading supplier of tooling materials. This is a position we have reached by improving our customers' everyday business. Long tradition combined with research and product development equips Uddeholm to solve any tooling problem that may arise. It is a challenging process, but the goal is clear – to be your number one partner and tool steel provider.

Our presence on every continent guarantees you the same high quality wherever you are. ASSAB is our wholly-owned subsidiary and exclusive sales channel, representing Uddeholm in the Asia Pacific area. Together we secure our position as the world's leading supplier of tooling materials. We act worldwide, so there is always an Uddeholm or ASSAB representative close at hand to give local advice and support. For us it is all a matter of trust – in long-term partnerships as well as in developing new products. Trust is something you earn, every day.

For more information, please visit [www.uddeholm.com](http://www.uddeholm.com), [www.assab.com](http://www.assab.com) or your local website.

UD  
WOR  
RUST IS SOM  
TRUST IS  
AUTOM  
KINDING SU  
TOUGHNESS STR  
MATERIALS  
EDDING WATER  
BYSTANDIN  
RESULTS. M  
CUSTOMER B  
BILITY TRUST IS  
AUTOMOTIVE  
LEADING SU  
INNOVATION  
STRENGTH INNOVATI  
WORLDWIDE PRE  
SOMETHING YO  
PROBLEM  
THE WORL  
NOMY THE  
DUCTILITY TO  
COMMITMENT PART  
KNOWLEDGE UP  
KNOWLEDGE  
RELIABI  
OF EXCE  
AUTOMOTIVE A  
ECONOMY THE  
TOTAL ECONOMY  
DUCTILITY TOUGHNE  
HARDNESS WORLDW  
TRUST IS SOMETH  
UNDERSTANDING MACHIN  
RESULTS. SOLVING PROB  
ECONOMY THE WORL  
STRENGTH IN  
TOUGHNESS STRENGTH  
MATERIALS PARTN  
UNDERSTANDING MACHIN  
BILITY RELIABILITY RESU  
LASTING TOOLS TOTAL  
YOU EARN, EVERY DAY. LO  
OF THINKING HIGH PE  
OFTOOLING MATERIALS  
INNOVATION KNOWLEDGE  
STRENGTH INNOVATION KNOW  
REFERENCE. LONG DURABILITY  
TRUST IS SOMETHING YOU EARN,  
PROBLEMS AUTOMOTIVE